

Dependence of critical current of spin transfer torque-driven magnetization dynamics on free layer thickness

Tomohiro Taniguchi^{1,2} and Hiroshi Imamura^{1*}

¹ Nanotechnology Research Institute, National Institute of Advanced Industrial Science and Technology, Central 2, 1-1-1, Umezono, Tsukuba, Ibaraki 305-8568, Japan

² Institute of Applied Physics, University of Tsukuba, Tsukuba, Ibaraki 305-8573, Japan
(Dated: February 3, 2009)

The dependence of the critical current of spin transfer torque-driven magnetization dynamics on the free-layer thickness was studied by taking into account both the finite penetration depth of the transverse spin current and spin pumping. We showed that the critical current remains finite in the zero-thickness limit of the free layer for both parallel and anti-parallel alignments. We also showed that the remaining value of the critical current of parallel to anti-parallel switching is larger than that of anti-parallel to parallel switching.

PACS numbers: Valid PACS appear here

Spin transfer torque (STT)-driven magnetization dynamics is a promising technique to operate spin-electronics devices such as a non-volatile magnetic random access memory (MRAM) and a microwave generator [1, 2]. STT is the torque due to the transfer of the transverse (perpendicular to magnetization) spin angular momentum from the conducting electrons to the magnetization of the ferromagnetic metal. One of the most important quantities of STT-driven magnetization dynamics is the critical current over which the dynamics of the magnetization is induced. The typical value of the critical current density is on the order of $10^6 - 10^8$ [A/cm²] [3, 4, 5]. Control of the value of the critical current is required to reduce the energy consumption of spin-electronics devices.

In Slonczewski's theory of STT [1], the critical current of P-to-AP (AP-to-P) switching is expressed as [6, 7]

$$I_c^{P \rightarrow AP(AP \rightarrow P)} = \frac{2eMSd}{\hbar\gamma\eta_{P(AP)}}\alpha_0\omega_{P(AP)}, \quad (1)$$

where e is the absolute value of the electron charge, $\hbar$ is the Dirac constant, and M , γ , S , d and α_0 are the magnetization, gyromagnetic ratio, cross section area, thickness and the intrinsic Gilbert damping constant of the free layer, respectively [5]. $\omega_{P(AP)}$ is the angular frequency of the magnetization around the equilibrium point. The coefficient $\eta_{P,AP}$ characterizes the strength of STT, and depends only on the relative angle of the magnetizations of the fixed and free layer [1, 6, 7]. According to Eq. (1), the critical current vanishes in the zero-thickness limit of the free layer, $d \rightarrow 0$.

However, recently, Chen *et al.* [5] reported that the critical current of STT-driven magnetization dynamics of a CPP-GMR spin valve remains finite even in the zero-thickness limit of the free layer. What are missed in the above naive considerations based on Slonczewski's theory are the effects of the finite penetration depth of the




FIG. 1: The schematic view of the nonmagnetic(N) / ferromagnetic(F) multilayer. I and I_s^{pump} are the electric current and pumped spin current, respectively. $I_s^{N_i(F_k)/N_j}$ is the spin current induced by the spin accumulations in each layer. $\mathbf{m}_k$ ($k = 1, 2$) is the unit vector pointing the direction of the magnetization of the F_k layer.

transverse spin current, λ_t , [8, 9, 10] and of spin pumping [11, 12, 13, 14]. We investigated the critical current of STT-driven magnetization switching from AP to P alignment by taking into account both the finite penetration depth of the transverse spin current and the spin pumping, and showed that the critical current remains finite in the zero-thickness limit of the free layer [15]. We also showed that the remaining value of the critical current is mainly determined by spin pumping. Although our results [15] agree well with the experimental results of Chen *et al.* [5], we investigated only the critical current of AP-to-P switching, $I_c^{AP \rightarrow P}$. For the manipulation of spin-electronics devices, the thickness dependence of the critical current of P-to-AP switching, $I_c^{P \rightarrow AP}$, should also be investigated.

In this paper, we study the critical current of STT-driven magnetization switching both from P to AP alignment and from AP to P alignment by taking into account both the finite penetration depth of the transverse spin current and the spin pumping. We show that both critical currents, $I_c^{P \rightarrow AP}$ and $I_c^{AP \rightarrow P}$, remain finite in the zero-thickness of the free layer. We also show that $I_c^{P \rightarrow AP}$ is larger than $I_c^{AP \rightarrow P}$ over the whole range of the free layer thickness, and thus, the remaining value of $I_c^{P \rightarrow AP}$ is larger than that of $I_c^{AP \rightarrow P}$. The difference between the remaining values of the critical currents, $I_c^{P \rightarrow AP}$ and $I_c^{AP \rightarrow P}$, can be explained by considering how the strength of STT, η , depends on the magnetic alignment.

A schematic view of the system we consider is shown

*Corresponding author. Email address: h-imamura@aist.go.jp

in Fig. 1. Two ferromagnetic layers (F_1 and F_2) are sandwiched by the nonmagnetic layers N_i ($i = 1 - 7$). The F_1 and F_2 layers correspond to the free and fixed layers, respectively. $\mathbf{m}_k$ ($k = 1, 2$) is the unit vector pointing in the direction of the magnetization of the F_k layer. I is the electric current flowing perpendicular to the film plane.

The electric current and pumped spin current at the F_k/N_i interface (into N_i) is obtained by using the circuit theory [12, 16]:

$$I^{F_k/N_i} = \frac{eg}{2h} [2(\mu_{F_k} - \mu_{N_i}) + p\mathbf{m}_k \cdot (\mu_{F_k} - \mu_{N_i})] , \quad (2)$$

$$\mathbf{I}_s^{\text{pump}} = \frac{\hbar}{4\pi} \left(g_r^{\uparrow\downarrow} \mathbf{m}_1 \times \frac{d\mathbf{m}_1}{dt} + g_i^{\uparrow\downarrow} \frac{d\mathbf{m}_1}{dt} \right) , \quad (3)$$

where $h = 2\pi\hbar$ is the Planck constant, $g = g^{\uparrow\uparrow} + g^{\uparrow\downarrow}$ is the sum of the spin-up and spin-down conductances, $p = (g^{\uparrow\uparrow} - g^{\uparrow\downarrow})/(g^{\uparrow\uparrow} + g^{\uparrow\downarrow})$ is the spin polarization of the conductances, and $g_{r(i)}$ is the real (imaginary) part of the mixing conductance. μ_{N_i, F_k} and μ_{N_i, F_k} are the charge and spin accumulation, respectively. The spin current at each F_k/N_i and N_i/N_j interface (into N_i) is given by [10, 16]

$$\begin{aligned} \mathbf{I}_s^{F_k/N_i} = & \frac{1}{4\pi} \left[g \left\{ p(\mu_{F_k} - \mu_{N_i}) + \frac{1}{2} \mathbf{m}_k \cdot (\mu_{F_k} - \mu_{N_i}) \right\} \mathbf{m}_k \right. \\ & - g_r^{\uparrow\downarrow} \mathbf{m}_k \times (\mu_{N_i} \times \mathbf{m}_k) - g_i^{\uparrow\downarrow} \mu_{N_i} \times \mathbf{m}_k \\ & \left. + t_r^{\uparrow\downarrow} \mathbf{m}_k \times (\mu_{F_k} \times \mathbf{m}_k) + t_i^{\uparrow\downarrow} \mu_{F_k} \times \mathbf{m}_k \right] , \end{aligned} \quad (4)$$

$$\mathbf{I}_s^{N_i/N_j} = -\frac{g_{N_i/N_j}}{4\pi} (\mu_{N_i} - \mu_{N_j}) , \quad (5)$$

where $t_{r(i)}^{\uparrow\downarrow}$ is the real (imaginary) part of the transmission mixing conductance at the F_k/N_i interface and g_{N_i/N_j} is the conductance of the one spin channel at the N_i/N_j interface.

The spin accumulations in the N and F layer obey the diffusion equation [8, 10, 17]. The spin accumulation in the N layer, μ_N , decays exponentially with the spin diffusion length $\lambda_{sd(N)}$. The longitudinal and transverse spin accumulations in the F layer are defined as $(\mathbf{m} \cdot \mu_F)\mathbf{m}$ and $\mathbf{m} \times (\mu_F \times \mathbf{m})$, respectively. The longitudinal and transverse spin accumulations decay exponentially with the spin diffusion length $\lambda_{sd(F_L)}$ and with the penetration depth of the transverse spin current λ_t , respectively.

The total spin currents across the N_3/F_1 and F_1/N_4 interfaces, i.e., $\mathbf{I}_s^{(1)} = \mathbf{I}_s^{\text{pump}} + \mathbf{I}_s^{F_1/N_3}$ and $\mathbf{I}_s^{(2)} = \mathbf{I}_s^{\text{pump}} + \mathbf{I}_s^{F_1/N_4}$, exert the torque $\boldsymbol{\tau} = \mathbf{m}_1 \times [(\mathbf{I}_s^{(1)} + \mathbf{I}_s^{(2)}) \times \mathbf{m}_1]$ on the magnetization $\mathbf{m}_1$. In order to obtain the spin current $\mathbf{I}_s^{(1,2)}$, we solve the diffusion equation of spin accumulation in each layer. The boundary conditions are as follows. We assume that the thicknesses of the N_1 and N_7 layer are much larger than their spin diffusion length, and that the spin current is zero at the outer boundary of the N_1 and N_7 layer. We also assume that the spin current is continuous at all interfaces and that the electric current is constant through the entire structure.

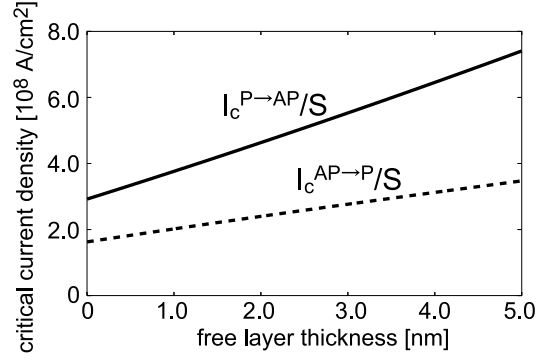


FIG. 2: The critical current densities of P-to-AP switching ($I_c^{P \rightarrow AP}/S$) and AP-to-P switching ($I_c^{AP \rightarrow P}/S$) in STT-driven magnetization dynamics are shown against the free layer thickness.

The torque $\boldsymbol{\tau}$ modifies the Landau-Lifshitz-Gilbert (LLG) equation of magnetization $\mathbf{m}_1$ as [12]

$$\begin{aligned} \frac{d\mathbf{m}_1}{dt} = & -\gamma \mathbf{m}_1 \times \mathbf{B}_{\text{eff}} + \frac{\gamma}{MSd} \boldsymbol{\tau} + \alpha_0 \mathbf{m}_1 \times \frac{d\mathbf{m}_1}{dt} \\ = & -\gamma_{\text{eff}} \mathbf{m}_1 \times \mathbf{B}_{\text{eff}} + \frac{\gamma_{\text{eff}}}{\gamma} (\alpha_0 + \alpha') \mathbf{m}_1 \times \frac{d\mathbf{m}_1}{dt} , \end{aligned} \quad (6)$$

where $\mathbf{B}_{\text{eff}}$ is the effective magnetic field, and $\alpha' = \alpha_c + \alpha_{\text{pump}}$ is the enhancement of the Gilbert damping constant. The enhancement α_c is proportional to the electric current and independent of the pumped spin current. The enhancement α_{pump} represents the contribution from the pumped spin current and is independent of the electric current. The enhancement of the gyromagnetic ratio, $\gamma_{\text{eff}}/\gamma$, is a function of both the electric current and the pumped spin current.

The critical current of the STT-driven magnetization dynamics is defined by the electric current that satisfies the condition, $\alpha_0 + \alpha_c + \alpha_{\text{pump}} = 0$, and given by

$$I_c^{P \rightarrow AP(AP \rightarrow P)} = \frac{2eMSd}{\hbar\gamma\tilde{\eta}_{P(AP)}} (\alpha_0 + \alpha_{\text{pump}}) \omega_{P(AP)} , \quad (7)$$

where the coefficient $\tilde{\eta}_{P,AP}$ characterizes the strength of STT due to the electric current, and is determined by the diffusion equations of the spin accumulations. Thus, $\tilde{\eta}_{P,AP}$ is the function of $d/\lambda_{sd(F_L)}$, d/λ_t and the relative angle of the magnetizations of the F_1 and F_2 layers.

We performed numerical calculation to obtain the critical currents $I_c^{P \rightarrow AP}$ and $I_c^{AP \rightarrow P}$. The system consists of nine layers as shown in Fig. 1, where F_1 and F_2 are Co, N_1, N_3, N_4, N_5 and N_7 are Cu, and N_2 and N_6 are Pt. The thicknesses of the N_3, N_4 and N_5 layers are 10 nm, the thicknesses of the N_2 and N_6 layers are 3 nm and the thickness of the F_2 layer is 12 nm [5]. The thickness of the N_1 and N_7 layers are taken to be 10 μm . The spin diffusion length of Cu and Pt are 1000 and 14 nm, respectively [18]. The conductance at the Cu/Pt interface is 35 nm^{-2} [18]. The magnetization, the intrinsic Gilbert damping constant and the gyromagnetic ratio of Co are

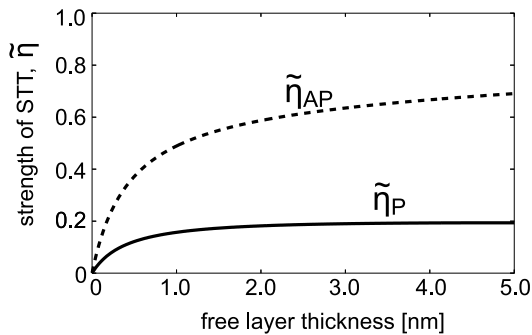


FIG. 3: The coefficient $\tilde{\eta}$ in the P state ($\tilde{\eta}_P$) and AP state ($\tilde{\eta}_{AP}$), against the free layer thickness.

0.14 T, 0.008 and 1.89×10^{11} Hz/T, respectively [5, 19]. The polarization p is taken to be 0.46 for Co [18]. The spin diffusion length of Co is 40 nm [18]. The penetration depth of the transverse spin current of Co is 4.2 nm [9, 15]. The conductances at the Co/Cu interface, g/S , $g_r^\uparrow/S$ and $g_i^\uparrow/S$, are 50, 27 and 0.4 nm^{-2} , respectively [12, 13, 16]. We assume that $t_r = t_i$ where $t_{r,i}/S$ at the Co/Cu interface is taken to be 6.0 nm^{-2} . The angular frequency is $\omega_{P(AP)} = \gamma[B_{\text{appl}} - (+)4\pi M]$ where the strength of the applied magnetic field B_{appl} is 7 T [5].

Figure 2 shows the dependence of the critical current density of Eq. (7) for P-to-AP switching, $I_c^{P \rightarrow AP}/S$, and AP-to-P switching, $I_c^{AP \rightarrow P}/S$, on the free layer thickness, d . As shown in Fig. 2, both $I_c^{P \rightarrow AP}$ and $I_c^{AP \rightarrow P}$ remain finite in the zero-thickness limit of the free layer. We show that the critical current $I_c^{P \rightarrow AP}$ is larger than $I_c^{AP \rightarrow P}$ over the whole range of the free layer thickness, and thus, the remaining value of $I_c^{P \rightarrow AP}$ is larger than

that of $I_c^{AP \rightarrow P}$. As shown in Ref. [15], the remaining value of the critical current is mainly determined by spin pumping. It should be noted that the magnitude of the enhancement of the Gilbert damping constant due to spin pumping, α_{pump} , is the same for both P-to-AP switching and AP-to-P switching [13, 14]. Thus, the fact that the remaining values $I_c^{P \rightarrow AP}$ and $I_c^{AP \rightarrow P}$ are different from each other implies that the strength of STT, $\tilde{\eta}_{P,AP}$, depends on the alignment of the magnetizations. As shown in Fig. 3, $\tilde{\eta}_{P,AP}$ decreases with a decreasing free layer thickness. On the other hand, the number of localized magnetic moments in the free layer, and therefore the STT per magnetic moment, is inversely proportional to the free layer thickness d . According to Eq. (7), the remaining value of the critical current is proportional to $(\tilde{\eta}_{P,AP}/d)^{-1}$ with $d \rightarrow 0$, where $\tilde{\eta}_P/d \simeq 0.44 \text{ nm}^{-1}$ and $\tilde{\eta}_{AP}/d \simeq 1.47 \text{ nm}^{-1}$ in the limit of $d \rightarrow 0$ are estimated by Fig. 3. Thus, the remaining value of $I_c^{P \rightarrow AP}$ is larger than that of $I_c^{AP \rightarrow P}$.

In summary, we studied the critical current of STT-driven magnetization dynamics by taking into account the finite penetration depth of the transverse spin current and spin pumping for both P and AP magnetic alignments. We showed that the critical current remains finite in the zero thickness limit of the free layer for both P-to-AP and AP-to-P switching. We also showed that the critical current for P-to-AP switching is larger than that for AP-to-P switching over the whole range of the free layer thickness.

The authors would like to acknowledge the valuable discussions they had with K. Matsushita, J. Sato and N. Yokoshi. This work was supported by JSPS and NEDO.

-
- [1] J. C. Slonczewski, J. Magn. Magn. Mater. **159**, L1 (1996).
 - [2] L. Berger, Phys. Rev. B **54**, 9353 (1996).
 - [3] S. I. Kiselev, J. C. Sankey, I. N. Krivorotov, N. C. Emley, R. J. Schoelkopf, R. A. Buhrman, and D. C. Ralph, Nature **425**, 380 (2003).
 - [4] T. Seki, S. Mitani, K. Yakushiji, and K. Takanashi, Appl. Phys. Lett. **89**, 172504 (2006).
 - [5] W. Chen, M. J. Rooks, N. Ruiz, J. Z. Sun, and A. D. Kent, Phys. Rev. B **74**, 144408 (2006).
 - [6] J. Z. Sun, Phys. Rev. B **62**, 570 (2000).
 - [7] J. Grollier, V. Cros, H. Jaffrés, A. Hamzic, J. M. George, G. Faini, J. B. Youssef, H. L. Gall, and A. Fert, Phys. Rev. B **67**, 174402 (2003).
 - [8] S. Zhang, P. M. Levy, and A. Fert, Phys. Rev. Lett. **88**, 236601 (2002).
 - [9] J. Zhang, P. M. Levy, S. Zhang, and V. Antropov, Phys. Rev. Lett. **93**, 256602 (2004).
 - [10] T. Taniguchi, S. Yakata, H. Imamura, and Y. Ando, Appl. Phys. Express **1**, 031302 (2008).
 - [11] S. Mizukami, Y. Ando, and T. Miyazaki, Phys. Rev. B **66**, 104413 (2002).
 - [12] Y. Tserkovnyak, A. Brataas, and G. E. W. Bauer, Phys. Rev. B **66**, 224403 (2002).
 - [13] Y. Tserkovnyak, A. Brataas, and G. E. W. Bauer, Phys. Rev. B **67**, 140404(R) (2003).
 - [14] T. Taniguchi and H. Imamura, Phys. Rev. B **76**, 092402 (2007).
 - [15] T. Taniguchi and H. Imamura, Phys. Rev. B **78**, 224421 (2008).
 - [16] A. Brataas, Y. V. Nazarov, and G. E. W. Bauer, Eur. Phys. J. B **22**, 99 (2001).
 - [17] T. Valet and A. Fert, Phys. Rev. B **48**, 7099 (1993).
 - [18] J. Bass and W. P. P. Jr, J. Phys.: Condens. Matter **19**, 183201 (2007).
 - [19] J.-M. L. Beaujour, W. Chen, A. D. Kent, and J. Z. Sun, J. Appl. Phys. **99**, 08N503 (2006).